

# GARBA 177 SUPREME

1/8

Precipitation hardenable stainless spring wire. Shaved and EC-tested\*. For applications demanding superior fatigue properties

GARBA 177 Supreme® is a semi-austenitic precipitation-hardenable stain-less steel, processed by ESR (Electro Slag Refining), which reduces the risk of harmful inclusions. The ESR process together with a shaved surface improves the fatigue resistance as compared to GARBA 177PH.

## CHEMISCHE ZUSAMMENSETZUNG

C (%)	Si (%)	Mn (%)	P max. (%)	S max. (%)	Cr (%)	Ni (%)	Al (%)
0,09	0,70	1,00	0,040	0,015	16,00 - 18,00	6,50 - 7,80	0,70 - 1,50

## REINHEITSGRAD IM STAHL

The presence of non-metallic inclusions in the wire rod is inspected for every heat in accordance with the Suzuki Garphyttan method by the steel supplier.

For wire rod samples: Inclusion size max. 15 µm down to 1 mm below surface. Inspection area: 350 mm<sup>2</sup>.

Inclusion size, surface	5-10	> 10-15	>15 µm
Max. number of inclusions	Max grade D3 acc. to JK scale*	20	0

\* Method for assessment of the content of non-metallic inclusions. Swedish Standard SS 111116 - Microscopic methods - Jernkontoret's inclusion chart II for the assessment of non-metallic inclusions.

# GARBA 177 SUPREME

2/8

## MECHANISCHE EIGENSCHAFTEN

### FÜR RUNDdraHT

Durchmesser (mm)	Toleranz (mm)	Zugfestigkeit (N/mm <sup>2</sup> )	Zugfestigkeit nach der Wärmebehandlung von 480C 1 Std. (N/mm <sup>2</sup> )
0,30 - 0,40	±0,005	1885 - 2165	2205 - 2525
0,41 - 0,50	±0,008	1860 - 2130	2180 - 2490
0,51 - 0,65	±0,008	1810 - 2070	2130 - 2430
0,66 - 0,80	±0,010	1810 - 2060	2130 - 2430
0,81 - 1,00	±0,010	1780 - 2030	2100 - 2390
1,01 - 1,25	±0,015	1720 - 1960	2040 - 2310
1,26 - 1,50	±0,015	1670 - 1910	1990 - 2260
1,51 - 1,75	±0,015	1610 - 1850	1910 - 2180
1,76 - 2,00	±0,015	1570 - 1800	1900 - 2160
2,01 - 2,50	±0,015	1540 - 1770	1860 - 2120
2,51 - 3,00	±0,020	1500 - 1710	1820 - 2060
3,01 - 3,50	±0,020	1400 - 1600	1660 - 1940
3,51 - 4,25	±0,020	1350 - 1550	1620 - 1920
4,26 - 5,00	±0,025	1310 - 1500	1580 - 1800
5,01 - 5,60	±0,025	1300 - 1490	1550 - 1790

## OBERFLÄCHENBESCHAFFENHEITEN

### Surface performance

AC-surface 0.30-5.60 mm Ø . The AC-coating can be removed before heat treatment by using a 10-20% nitric acid pickle at room temperature.

### OBERFLÄCHENBESCHAFFENHEIT

#### Surface condition – non-destructive testing

In the standard size range 2.00-5,60 mm the wire can be tested continuously in Eddy Current equipment to a surface level of >40 microns.

# GARBA 177 SUPREME

3/8

## PHYSIKALISCHE EIGENSCHAFTEN

### E UND G ELASTIZITÄTSMODUL

Abt. 190 kN/mm<sup>2</sup> in drawn condition.  
Abt. 200 kN/mm<sup>2</sup> after heat treatment.

### E UND G SCHUBMODUL

Abt. 73 kN/mm<sup>2</sup> in drawn condition.  
Abt. 78 kN/mm<sup>2</sup> after heat treatment.  
Density: 7.90 kg/dm<sup>3</sup>.

### WÄRMELEITFÄHIGKEIT

Temperature °C	20	100	300
W/(m*°C)	15.0	15.5	19.0

### WIDERSTANDSFÄHIGKEIT

Temperature °C	20	100	200	300
nΩm	900	950	1000	1050

### LÄNGENAUSDEHNUNG

Pro °C	30-100	30-200	30-300
x10 <sup>-6</sup>	13.0	13.5	14.0

### SPEZIFISCHE WÄRMEKAPAZITÄT

Temperature °C	100	200
J/(kg*°C)	480	520

## STANDARDS

### NÄCHSTÄHNLICHE VERGLEICHBARE STAHLGÜTEN

EN/DIN 1.4568, AISI/SAE 631, JIS SUS 631

### NÄCHSTÄHNLICHE VERGLEICHBARE NORMEN

EN 10270-3, ASTM A313, AMS 5678, BS 2056 301 S81, JIS G4314


## EMPFEHLUNGEN

### Electro slag refining (ESR) process

For further technical support, please contact Suzuki Garphyttan or visit [www.suzuki-garphyttan.com](http://www.suzuki-garphyttan.com) for more information

# GARBA 177 SUPREME

For applications demanding superior fatigue properties

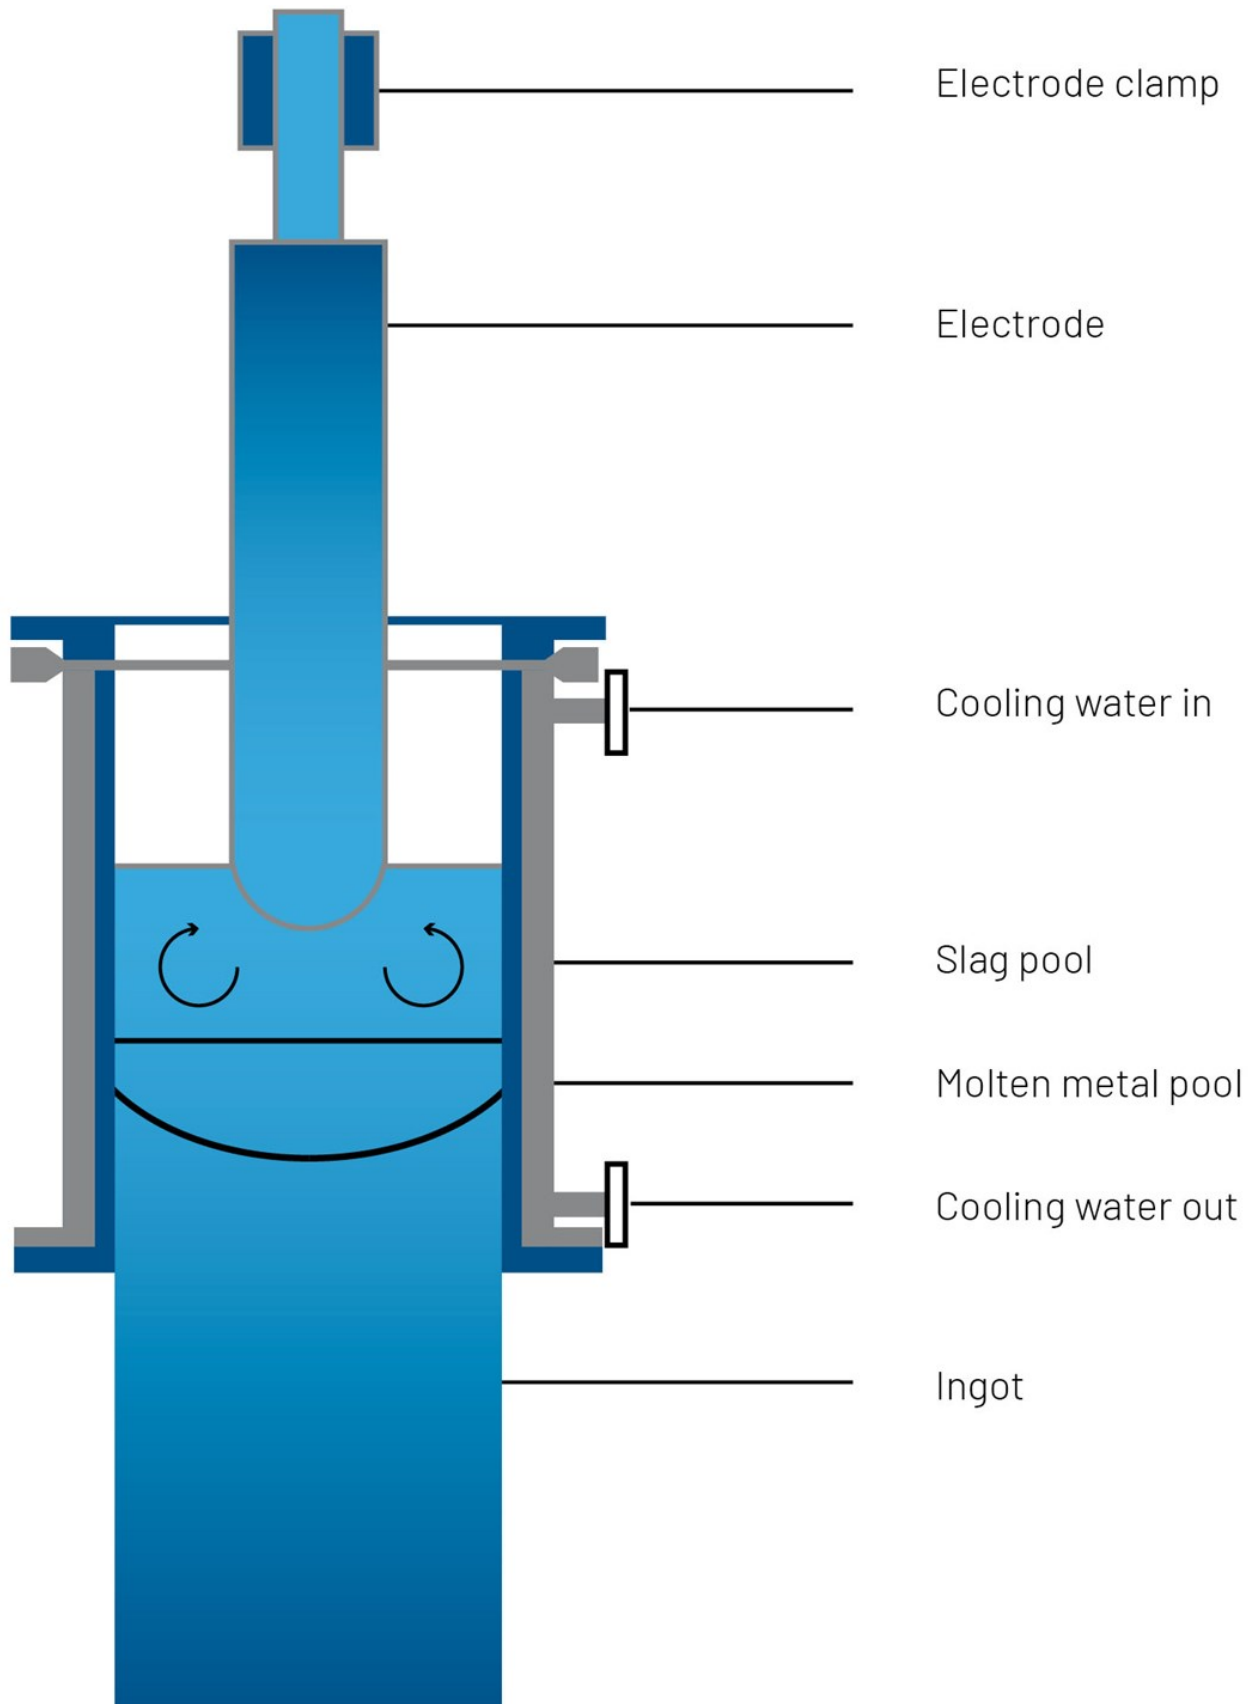

# GARBA 177 SUPREME

5/8



Starting plate

Water cooling

Electro Slag Refining (ESR) process

ESR process, see figure 1.

The ESR process gives a material with lower level of inclusions compared to a material not processed with ESR and in addition also a better segregation level.

Material properties achieved by ESR in combination with shaved wire surface and precipitation hardening result in superior fatigue resistance.

Shaved and Eddy Current tested

Suzuki Garphyttan uses the most advanced Eddy Current testing equipment available on the market. Experience from many years of surface testing in efficient continuous testing lines is a guarantee for high quality spring wire.

Eddy Current testing is carried out on material with high demands on surface quality. EC-testing is performed with both rotating (R) and stationary (D) probe test equipment.

Steel grade	Dimension, mm	ESR	Shaved	Unshaved	RD40
GARBA 177 Supreme®	0.30 - 1.99	x	x	-	-
GARBA 177 Supreme®	2.00 - 5.60	x	x	-	x

Steel grade Dimension, mm ESR Shaved Unshaved RD40

GARBA 177 Supreme® 0.30 - 1.99 X X - -

GARBA 177 Supreme® 2.00 - 5.60 X X - X

## WÄRMEBEHANDLUNG

Normal procedure for precipitation hardening is heat treatment at 480oC (896oF) for 1 hour and then air cooling. This should be done as soon as possible after spring coiling. The tensile strength of the wire before and after this treatment is given in the table in previous page.


## KUGELSTRAHLEN

In order to obtain optimum fatigue properties, the process time should be adjusted to get a complete treatment. Size of shots should be adapted to wire dimension, pitch and shot peening equipment.

Shot peening of the inside of the spring coils is particularly critical.


## RELAXATIONS- UND ERMÜDUNGSEIGENSCHAFTEN

# GARBA 177 SUPREME

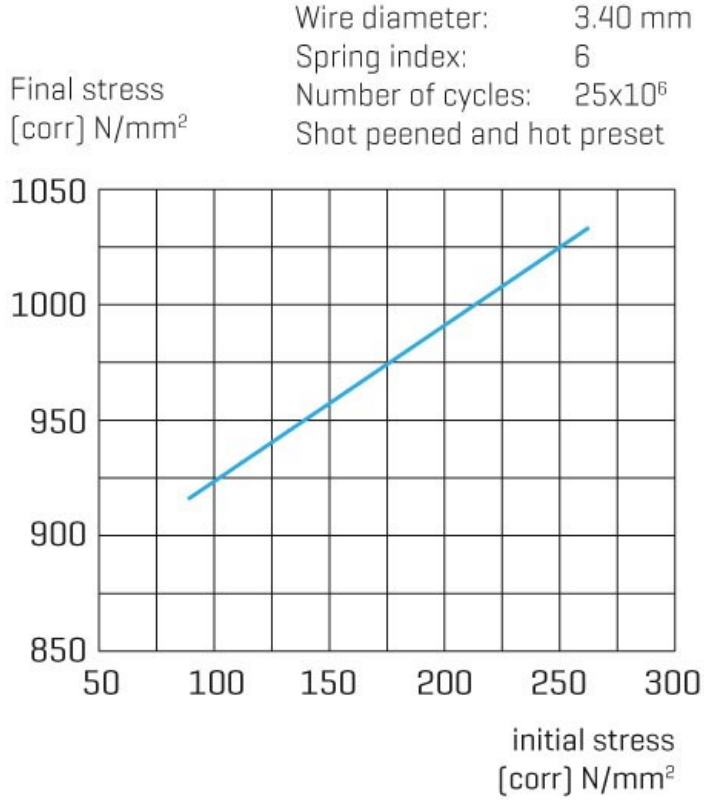

In diagram 1 the fatigue properties of GARBA 177 Supreme<sup>®</sup> is illustrated in a Goodman-diagram, based on a special test spring design.

# GARBA 177 SUPREME

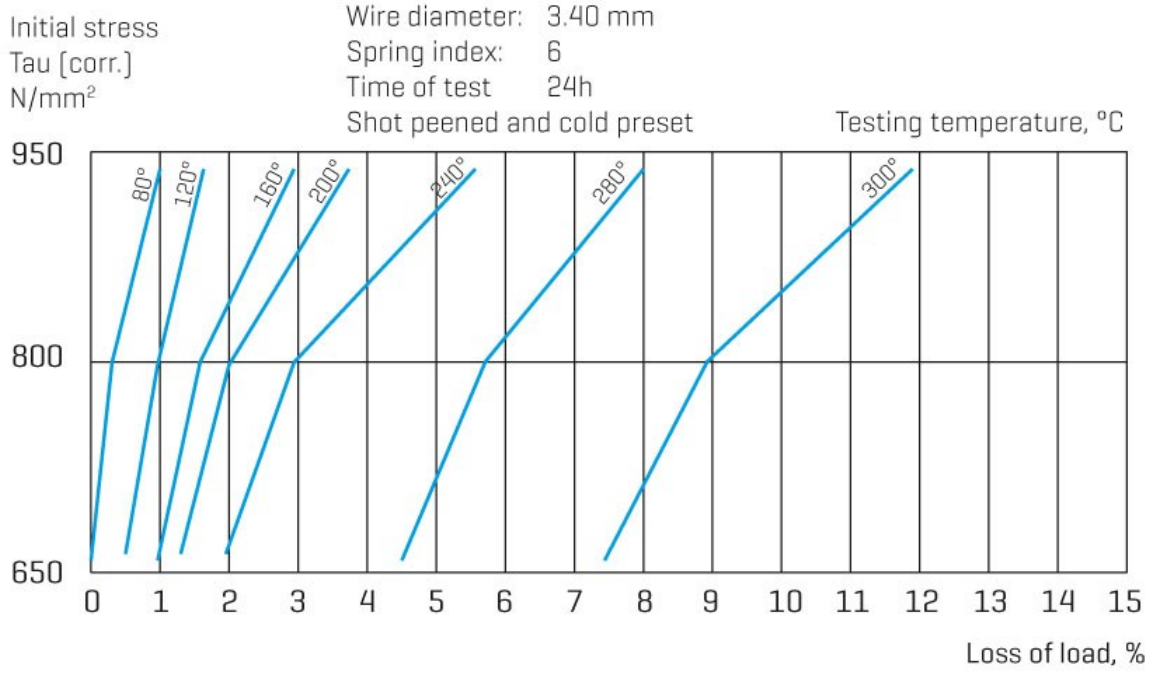

# GARBA 177 SUPREME

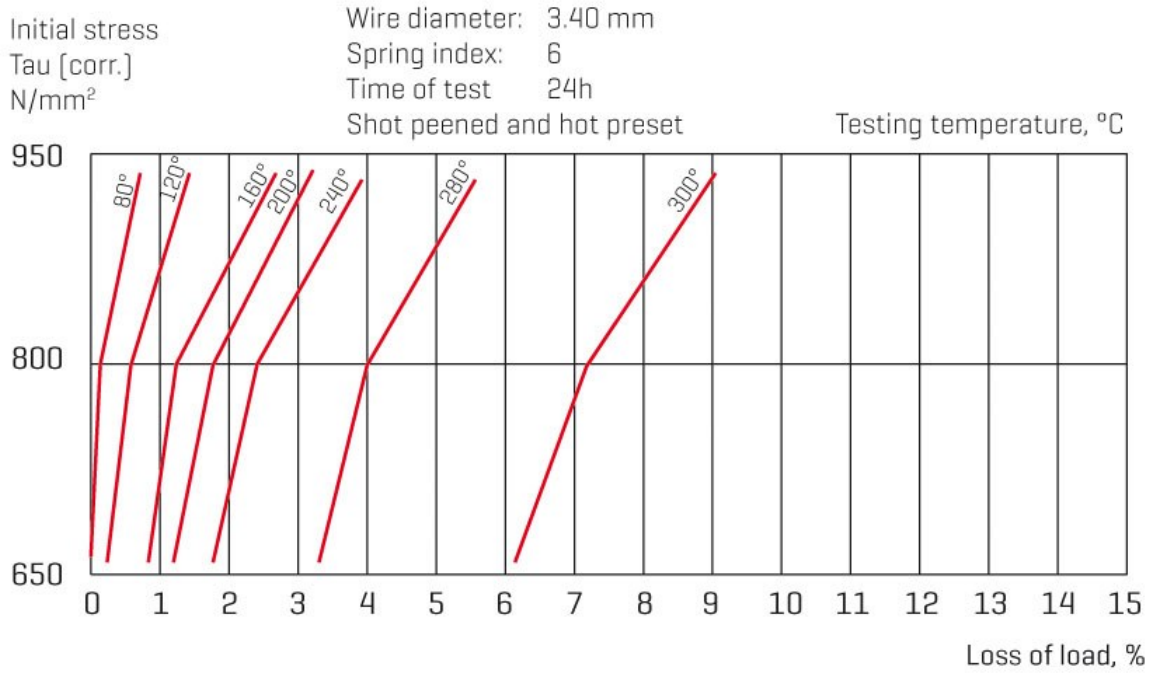


Diagram 2-3 show the relaxation properties (loss of load) of springs made from GARBA 177 Supreme<sup>®</sup> subjected to three different stress levels at different temperatures.